

# Removal and Reusability of Lead (II) from Aqueous Samples Using the Adsorption Method onto Commercial Activated Carbon: Kinetics and Thermodynamics Studies

Yahya S. Alqahtani<sup>1,\*</sup>, Samer S. Abu Al-Rub<sup>1</sup>, Ali O. Alqarni<sup>1</sup>, Mater H. Mahnashi<sup>1</sup>, Bandar A. Alyami<sup>1</sup>, Meriem Rezigue<sup>2</sup>

<sup>1</sup>Department of Pharmaceutical Chemistry, College of Pharmacy, Najran University, Najran, SAUDI ARABIA.

<sup>2</sup>Department of Pharmaceutics and Pharmaceutical Technology, Faculty of Pharmacy, Yarmouk University, Irbid, JORDAN.

## ABSTRACT

**Background and Aim:** The study focused on the sorption of lead  $Pb^{2+}$  from water samples using Commercial Activated Carbon (CAC) sorbent. **Materials and Methods:** The factors affecting the absorbance between  $Pb^{2+}$  and CAC were examined the mass of the CAC, ionic strength, pH solution and effect of temperature on the solution. Isotherm models (Langmuir, Freundlich and Temkin) were examined for  $Pb^{2+}$  adsorption on CAC. **Results and Discussion:** Freundlich isotherm model was determined as the best lead adsorption model on CAC. Freundlich model parameters  $R^2$ ,  $n$ , and  $k_f$  were found 0.9889, 1.48, 0.53  $mg.g^{-1}$  respectively. The adsorption capacity ( $q_e$ ) was 12.81  $mg.g^{-1}$ . Thermodynamic parameters  $\Delta H$ , and  $\Delta S$  were found -1422.8 and 5.2389  $KJ.mol^{-1}$  respectively. The adsorption process was exothermic. A Pseudo-Second-Order (PSO) model was followed for the adsorption process. Finally, the method was proved to be highly effective method for the extraction of the  $Pb^{2+}$  using CAC three times. The percentage extractions (%ER) found ranged from 107.0-91.9 % for stimulation marketing drink water and tap water. **Conclusion:** CAC is distinguished as an adsorbent that excels other adsorbents in removing the  $Pb^{2+}$  from aqueous solutions due to its chemical and physical properties.

**Keywords:** Lead (II), Commercial activated carbon (CAC), Thermodynamics, Adsorption isotherm models, Kinetics models.

## Correspondence:

**Dr. Yahya S. Alqahtani**

Associate Professor, Department of Pharmaceutical Chemistry, College of Pharmacy, Najran University, Najran-66462, SAUDI ARABIA.  
Email: ysalqahtaniy@gmail.com

**Received:** 10-06-2023;

**Revised:** 28-10-2023;

**Accepted:** 09-01-2024.

## INTRODUCTION

Toxic heavy metals in aqueous solutions pose a serious threat to the environment, such as lead, ( $Pb^{2+}$ ).<sup>1</sup> The high concentration of lead element in aqueous solution above the permissible limits endangers the life of the consumer.<sup>2</sup> This metal can be discharged into abrasive solution from various industries, including metal plating, storage batteries, alloying industries, fertilizer and other chemical industries.<sup>3,4</sup> The researchers were interested in removing heavy metals from the aqueous solution by various methods, including adsorption, chemical precipitation, and ion exchange, due to the importance of preserving the aquatic environment with the increase of industrial activities.<sup>5-7</sup> Adsorption is one of the most common processes applied in the purification of aqueous solutions of heavy metals.<sup>8</sup> Lead is a major concern to children due to its environmental source in

developing countries.<sup>8</sup> The toxicity of lead metal comes from various human related activities such as smoking, leaded car fuel, contaminated food, ground water, houses painting and drinking water.<sup>9,10</sup> Excessive exposure of children to lead affects the functions of the body causing headache, vomiting, neurons diseases, heart diseases, blood diseases In case children exposed to a high percentage of lead, they suffer an encephalopathy as a result of failure in the performance of the Central Nervous System (CNS).<sup>11-13</sup> Adsorption is one of the most suitable processes for treatment aqueous solutions of metal ions. When a solute liquid accumulates on the surface of the absorbent material, forming an adsorbent, the process is called adsorption.<sup>14</sup> Adsorption is one of the most suitable processes for treatment aqueous solutions of metal ions. The adsorption technology is characterized by ease of use, efficiency and low cost.<sup>15,16</sup> Activated Carbon (AC) is a carbon containing substance produced from organic materials. CAC is classified on the basis of their shape and size and is in the form of pellets or powder.<sup>17,18</sup> CAC's composition containing on different functional groups and medium pores.<sup>19</sup> The surface area of CAC ranges from 500 to 3000  $m^2.g^{-1}$ .<sup>19,20</sup> It is used in the treatment of aqueous solutions, recovery of solvents and pharmaceutical industry.<sup>19</sup> CAC has functional groups like carbonyl, phenols,



DOI: 10.5530/ijper.58.2.49

### Copyright Information :

Copyright Author (s) 2024 Distributed under  
Creative Commons CC-BY 4.0

Publishing Partner : EManuscript Tech. [www.emanuscript.in]

quinones, carboxyl, and lactones that play a role in the adsorption of heavy metals from polluted aqueous solutions.<sup>21,22</sup>

## MATERIALS AND METHODS

### Chemicals and Apparatus

This project used only analytical-grade chemicals. The lead nitrate,  $\text{Pb}(\text{NO}_3)_2$  was obtained from sigma Aldrich and CAC 300-500  $\mu\text{m}$ , from Nen. Tech Ltd., (UK), with a surface area of 500-3000  $\text{m}^2.\text{g}^{-1}$  and the overall capacity of the pores of 1.4  $\text{cm}^3.\text{g}^{-1}$ . UV-vis spectrophotometer was used to obtain the absorption spectra (SP-3000 nano, Optima, Japan) and pH measurements were performed using an Ezdo pH-pp-201 (Taiwan). In this work, a water bath shaker (Daihan Scientific, Korea) was used.

### Procedure

The quantity of  $\text{Pb}^{2+}$  that was adsorbed by the CAC was determined through calculation. The impacts of the CAC on the adsorption parameters like concentrations of  $\text{Pb}^{2+}$ , pH solution, mass, ionic strength, and temperature was investigated. A set of various concentrations ranging from 0.1-1.0  $\mu\text{g}.\text{L}^{-1}$ , a linear calibration curve was obtained at 340 nm to calculate the final  $\text{Pb}^{2+}$  concentrations in the solution using a spectrophotometer. The  $R^2=0.9907$  was obtained.

### Effect of contact time, mass, pH of solution and ionic strength

The effect of time was studied by calculating the final  $\text{Pb}^{2+}$  concentration in the solution. 100 mg CAC was added to 50 mL solutions containing a primary concentration of 0.55  $\mu\text{g}.\text{L}^{-1}$   $\text{Pb}^{2+}$  and stirred for 5 to 30 min at 25°C. The effect of CAC mass on aqueous solutions under agitation time conditions was studied using a series of CAC mass (50 to 1000 mg). The effect of pH on aqueous solutions under agitation time conditions was studied using a series of pH (1.0 to 12.0). The ionic strength effect on aqueous solutions under agitation time conditions was examined via several concentrations of NaCl (0.5-2.0 M). The final of  $\text{Pb}^{2+}$  concentration was determined.

### Adsorption isotherms

The isothermal adsorption impacts of CAC adsorbent were examined at varying concentrations (0.15-0.95  $\mu\text{g}.\text{L}^{-1}$ ) of  $\text{Pb}^{2+}$  in water solutions, by adding 100 mg of AC, at pH 7 and at different concentrations of  $\text{Pb}^{2+}$  (0.15 to 0.95  $\mu\text{g}.\text{L}^{-1}$ ). The solutions were stirred at different concentrations at various temperatures (298, 303, 313 and 323K). The  $\text{Pb}^{2+}$  adsorbent concentration and distribution coefficient were calculated according to Equation formula 1.

$$q_e = \frac{(C_i - C_f)}{m} \times V \dots\dots\dots (1)$$

Where the  $q_e$  quantity of adsorbed ( $\text{mg}.\text{g}^{-1}$ ), initial ( $C_i$ ,  $\mu\text{g}.\text{L}^{-1}$ ), the equilibrium ( $C_f$ ,  $\mu\text{g}.\text{L}^{-1}$ )  $\text{Pb}^{2+}$  concentration,  $m$  is adsorbent mass (mg).

## RESULTS AND DISCUSSION

### Effect of contact time, mass of CAC, pH, ionic strength, $\text{Pb}^{2+}$ concentration, and Temperature

According to Figure 1a, the % removal of  $\text{Pb}^{2+}$  was based on the quantity of CAC present in the solution. When the quantity of CAC increased, the % removal of the  $\text{Pb}^{2+}$  increased; the figure shows that the % removal changes little for masses greater than 100 mg. As Figure 1b shows, in the neutral solution, the % removal of  $\text{Pb}^{2+}$  increased, but the % removal decreased from 41% in acidic medium (at pH 1) to 30% in basic medium (at pH 12). Figure 1c shows that the percentage removal (% removal) of  $\text{Pb}^{2+}$  increased with time. The contact time was adjusted at 15 min, it is better to keep the contact time short for economic reasons.<sup>23</sup> As Figure 1d shows, the % removal of  $\text{Pb}^{2+}$  in the solution decreased with increasing concentrations, reaching 47% at 0.95  $\mu\text{g}.\text{L}^{-1}$  and 79% at 0.15  $\mu\text{g}.\text{L}^{-1}$ . The % removal values were slightly decreased at a concentration of 0.55  $\mu\text{g}.\text{L}^{-1}$ . The decrease in the adsorption process of  $\text{Pb}^{2+}$  is due to the decrease in the active sites for CAC. Figure 1d shows that the distribution coefficient of  $\text{Pb}^{2+}$  decreased with increasing temperature, which indicates that the process is exothermic. The effect of temperature on the surface of the CAC indicates the destruction of active sites, which led to an increase in the adsorption of  $\text{Pb}^{2+}$ .

### Adsorption isotherm


To determine the ability of CAC to absorb  $\text{Pb}^{2+}$  from aqueous solutions the Langmuir, Temkin and Freundlich models were used. Table 1 shows that Freundlich's model is the best for adsorption of  $\text{Pb}^{2+}$  and CAC, indicating that the adsorption is heterogeneous. Table 1 also shows the  $R^2$  values for both the Langmuir and Temkin models. The values indicate that the two models are less suitable. Table 1 shows the  $n$  values in the Freundlich  $\text{Pb}^{2+}$  absorption model (1.4806 to 1.9689  $\mu\text{g}.\text{L}^{-1}$ ). Both values of  $A$  and  $B$  in Temkin's model showed that the reaction resulting from adsorption of  $\text{Pb}^{2+}$  and CAC is a physical adsorption.

### Adsorption thermodynamic parameters and kinetic models

Enthalpy and entropy were used to determine the adsorption of  $\text{Pb}^{2+}$  from CAC through equation formula 2.

$$\ln kd = \frac{\Delta S}{R} - \frac{\Delta H}{RT} \dots\dots\dots (2)$$

Where the  $\Delta H$  enthalpy ( $\text{KJ}.\text{mol}^{-1}$ ),  $R$  gas constant is (8.3145  $\text{J}.\text{mol}^{-1}.\text{K}^{-1}$ ),  $\Delta S$  entropy ( $\text{J}.\text{K}^{-1}.\text{mol}^{-1}$ ), and  $kd$  distribution coefficient. The values of  $\Delta H^\circ$  and  $\Delta S^\circ$  were found to be -1422.8 and 5.2389, respectively, as represented in Table 2. The adsorption process of the  $\text{Pb}^{2+}$  onto CAC was not spontaneous,

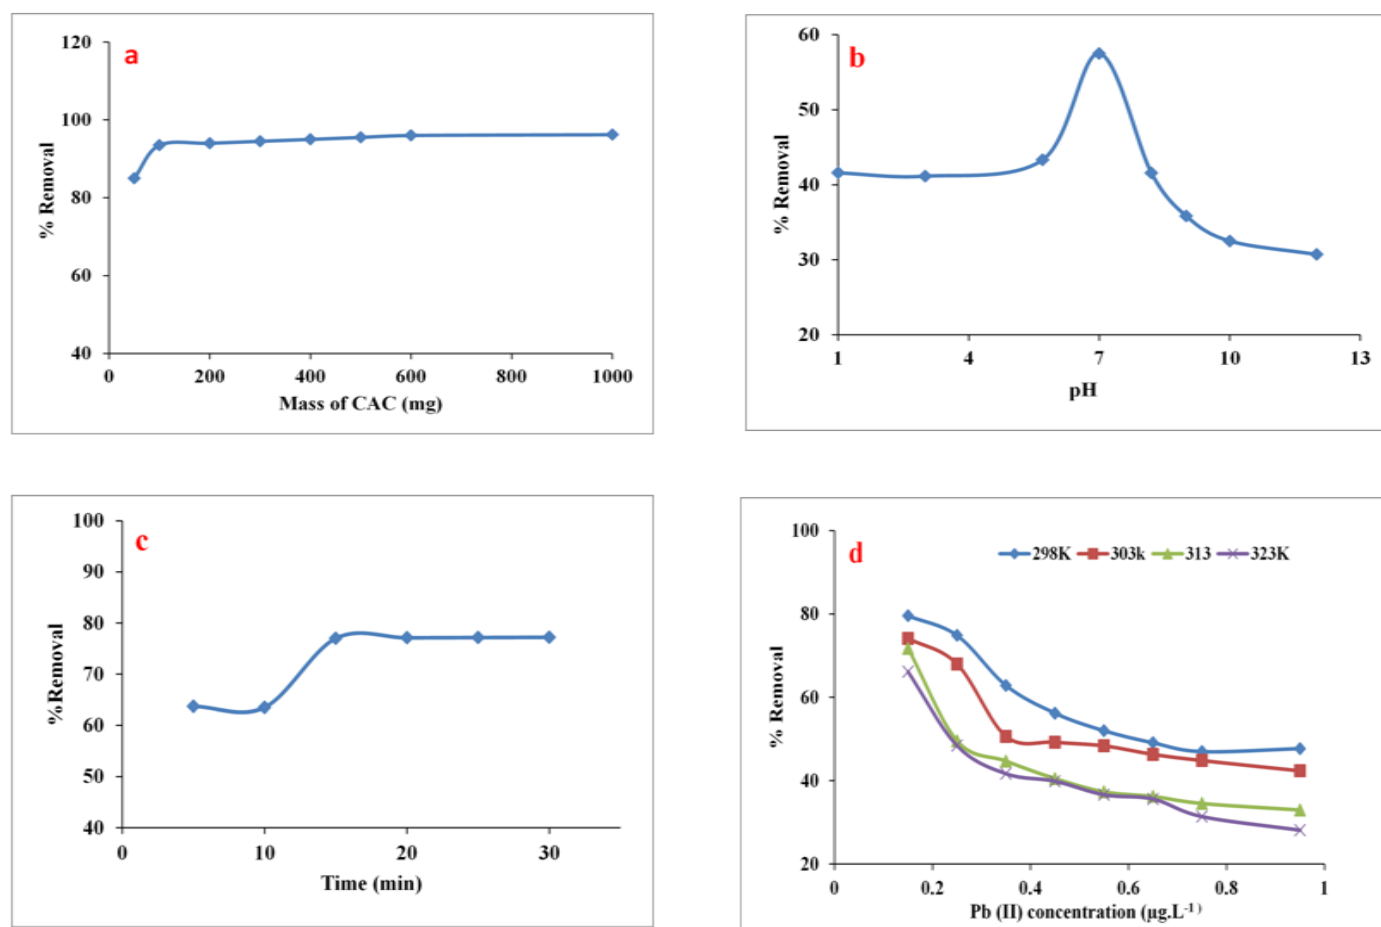


**Figure 1:** Impact of contact time (a), mass of CAC (b), pH (c), ionic strength (d), concentration, and temperature on the % removal of Pb<sup>2+</sup> onto CAC.

and exothermic due to the positive value of  $\Delta G$ , and the negative value of  $\Delta H^\circ$ . The adsorption of Pb<sup>2+</sup> onto CAC was highly random during the solid-liquid interface due to the positive value of the  $\Delta S^\circ$ . The values of ( $\Delta G$ ) increase with increasing the temperature, which indicates that the adsorption of Pb<sup>2+</sup> with CAC was exothermic.

First Pseudo Order (FPO) and Second Pseudo Order (SPO) were used to examine kinetic models to assess Pb<sup>2+</sup> adsorption in AC. Table 3 shows that the  $q_{e \text{ exp.}}$  value (mg.g<sup>-1</sup>) is not close to the  $q_{e \text{ cal.}}$  value (mg.g<sup>-1</sup>), the  $R^2=0.9673$  indicates that the FPO does not correspond to the sorption of Pb<sup>2+</sup> in the CAC. The experimental value of  $q_e$  is consistent with the calculated " $q_e$ " and  $R^2=0.9954$  indicates that SPO corresponds to Pb<sup>2+</sup> adsorption in the CAC.

### Reusability of CAC to remove Pb<sup>2+</sup>

The reuse of the CAC to extract Pb<sup>2+</sup> was examined in an aqueous solution. Figure 2 shows the values of reuse of the CAC (97.21%, 81.19%, and 73.36%), respectively, showing that the CAC can extract the Pb<sup>2+</sup> after three cycles.

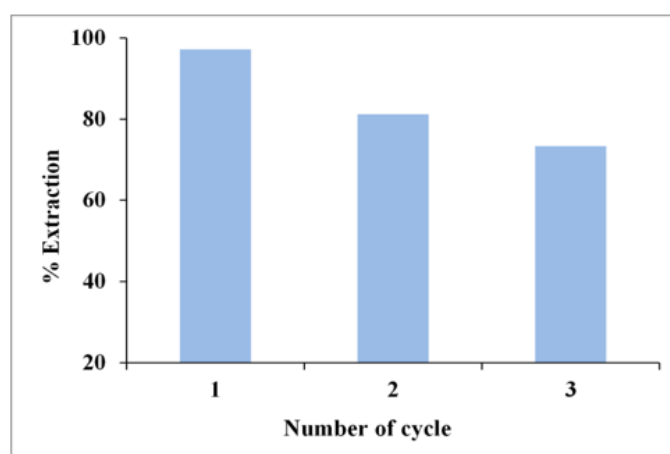

**Figure 2:** Reuse to extraction of Pb<sup>2+</sup> using CAC.

### Water sample applications

The percentage of extraction recovery (%ER) of Pb<sup>2+</sup> was determined in tap water samples and marketing drink water samples. The % ER ranged from 107.0- 92.4% and 102.7-91.9% in marketing drink water and tap water samples, respectively, as represented in Table 4.

**Table 1:** Isotherm parameters of Langmuir, Freundlich, and Temkin models.

Langmuir				Freundlich			Temkin		
T.(K)	R <sup>2</sup>	q <sub>max</sub>	kl	R <sup>2</sup>	kf	n	R <sup>2</sup>	A	B
298	0.8041	12.814	1.1077	0.9889	0.3586	1.4806	0.9306	12.2803	0.1598
303	0.7308	6.9909	0.1094	0.9500	0.5847	1.6823	0.9261	14.7052	1.3247
313	0.7030	6.3557	0.1102	0.9880	0.6541	1.5288	0.9192	17.8410	1.3626
323	0.8406	4.5735	0.1552	0.9551	0.5079	1.9689	0.9606	18.5524	1.0324

**Table 2:** Thermodynamic parameters for the adsorption of Pb<sup>2+</sup> onto CAC.

ΔH	ΔS	ΔG (kJ.mol <sup>-1</sup> )			
		298 K	303 K	313 K	323K
-1422.8	5.2389	138.4	191.9	216.9	298.4

**Table 3:** Kinetic parameters for PFO and PSO models.

Pb <sup>2+</sup> conc. (μg.L <sup>-1</sup> )	Pseudo-First-order (PFO)			Pseudo-Second-order (PSO)		
0.55	k <sub>1</sub> (min <sup>-1</sup> )	q <sub>e</sub> cal. (mg.g <sup>-1</sup> )	R <sup>2</sup>	k <sub>2</sub> (g.mg <sup>-1</sup> .min <sup>-1</sup> )	q <sub>e</sub> cal. (mg.g <sup>-1</sup> )	R <sup>2</sup>
	0.004	3.1485	0.9673	31.6	0.013	0.9954

**Table 4:** Percentage extraction recovery of Pb<sup>2+</sup> from marketing drinks water and tap water samples.

Sample	Added (μg.L <sup>-1</sup> ) (μg.mL <sup>-1</sup> ) (μM)	Found (μg.mL <sup>-1</sup> )	% ER ± SD
Marketing drink water samples	1	0.96	96.0±1.15
	2	2.14	107.0±0.92
	3	2.94	98.2±1.36
	4	4.052	101.3±0.86
	5	4.705	94.1±0.55
Tap water samples	1	0.924	92.4±1.33
	2	1.948	97.4±1.05
	3	3.081	102.7±0.91
	4	3.944	98.6±0.75
	5	4.595	91.9±0.82

## CONCLUSION

This study focuses on the environmental aspect of removing toxic Pb<sup>2+</sup> from solution by using CAC as adsorbent. The adsorption capacity (q<sub>e</sub>) of the Pb<sup>2+</sup> on CAC was 12.81 at pH 7, 100 mg of CAC, and 25°C. The equilibrium adsorption data were better suited to

the Freundlich isotherm model using an adsorption isotherm for Pb<sup>2+</sup> on CAC. Positive ΔG, negative ΔH, and positive ΔS were found to indicate the adsorption process is non-spontaneous, exothermic, and random, respectively. The PSO kinetic model was obeyed for the adsorption of Pb<sup>2+</sup> with CAC. The CAC can extract Pb<sup>2+</sup> from an aqueous solution after three times.

## ACKNOWLEDGEMENT

The authors are thankful to the Deanship of Scientific Research at Najran University for funding this work under the Research Group Funding program grant code (NU/RG/MRC/12/4).

## CONFLICT OF INTEREST

The authors declare that there is no conflict of interest.

## REFERENCES

- Kuyucak N, Volesky BJB. Biosorbents for recovery of metals from industrial solutions. *Biotechnol Lett.* 1988; 10(2): 137-42. doi: 10.1007/BF01024641.
- Wang H, Tang H, Liu Z, Zhang X, Hao Z, Liu ZJJ o. E.S., Removal of cobalt (II) ion from aqueous solution by chitosan-montmorillonite. 2014; 26(9): 1879-84.
- Wu Q, Leung JY, Geng X, Chen S, Huang X, Li H, *et al.* o.t. T.E., heavy metal contamination of soil and water in the vicinity of an abandoned e-waste recycling site: implications for dissemination of heavy metals. 2015; 506: 217-25.
- Al-Omar MA, El-Sharkawy EA. Removal of heavy metals via adsorption on activated carbon synthesized from solid wastes. *Environ Technol.* 2007; 28(4): 443-51. doi: 10.1080/09593332808618808, PMID 17500319.
- Jang A, Seo Y, Bishop PLJE. The removal of heavy metals in urban runoff by sorption on mulch. *Environ Pollut.* 2005; 133(1): 117-27. doi: 10.1016/j.envpol.2004.05.020, PMID 15327862.
- Kara M, Yuzer H, Sabah E, Celik MS. Adsorption of cobalt from aqueous solutions onto sepiolite. *Water Res.* 2003; 37(1): 224-32. doi: 10.1016/s0043-1354(02)00265-8, PMID 12465804.
- Moon CJ, Lee J-hJP. Use of curdlan and activated carbon composed adsorbents for heavy metal removal. *Process Biochemistry.* 2005; 40(3-4): 1279-83. doi: 10.1016/j.procbio.2004.05.009.
- Debnath B, Singh WS, Manna KJJ. Sources and toxicological effects of lead on human health. 2019; 10(2): 66.
- Naranjo VI, Hendricks M, Jones KSJPN. Lead toxicity in children: an unremitting public health problem. *Pediatr Neurol.* 2020; 113: 51-5. doi: 10.1016/j.pediatrneuro.2020.08.005, PMID 33011642.
- World health organization. WHO chemical safety: activity report 2018. World Health Organization; 2019.
- Pal M, Sachdeva M, Gupta N, Mishra P, Yadav M, Tiwari AJB. Lead exposure in different organs of mammals and prevention by curcumin-nanocurcumin: a review. *Biol Trace Elem Res.* 2015; 168(2): 380-91. doi: 10.1007/s12011-015-0366-8, PMID 26005056.
- Vasquez MA, Cruz GB, Cabañas E, Joseph JN, Mian M, Madhira SKV, *et al.* *In vivo* sex-dependent effects of perinatal Pb2+ exposure on pilocarpine-induced seizure susceptibility and taurine neuropharmacology. In: Taurine 12: A conditionally essential amino acid. Springer; 2022. p. 481-96. doi: 10.1007/978-3-030-93337-1\_44, PMID 35882820.
- Alluri HK, Ronda SR, Settalluri VS, Bondili JS, Suryanarayana V, Venkateshwar PJA j. o. B. Biosorption: an eco-friendly alternative for heavy metal removal. 2007; 6(25).
- Yadanaparthi SKR, Graybill D, von Wandruszka RJJ. Adsorbents for the removal of arsenic, cadmium, and lead from contaminated waters. *J Hazard Mater.* 2009; 171(1-3): 1-15. doi: 10.1016/j.jhazmat.2009.05.103, PMID 19540667.
- Kwon JS, Yun S-T, Lee J-H, Kim S-O, Jo HYJJ. H.M., Removal of divalent heavy metals (Cd, Cu, Pb, and Zn) and arsenic (III) from aqueous solutions using scoria: kinetics and equilibria of sorption. *Journal of Hazardous Materials.* 2010; 174(1-3): 307-13. doi: 10.1016/j.jhazmat.2009.09.052.
- Lakherwal DJI j. o. e. r. development, Adsorption of heavy metals: a review. 2014; 4(1): 41-8.
- Ani JU, Akpomie KG, Okoro UC, Aneke LE, Onukwuli OD, Ujam OT. Potentials of activated carbon produced from biomass materials for sequestration of dyes, heavy metals, and crude oil components from aqueous environment. *Appl Water Sci.* 2020; 10(2): 1-11. doi: 10.1007/s13201-020-1149-8.
- Hsia B, Kim MS, Vincent M, Carraro C, Maboudian RJC. Photoresist-derived porous carbon for on-chip micro-supercapacitors. *Carbon.* 2013; 57: 395-400. doi: 10.1016/j.carbon.2013.01.089.
- Yang K, Peng J, Srinivasakannan C, Zhang L, Xia H, Duan XJB. Preparation of high surface area activated carbon from coconut shells using microwave heating. *Bioresour Technol.* 2010; 101(15): 6163-9. doi: 10.1016/j.biortech.2010.03.001, PMID 20303745.
- Le Van K, Luong Thi TTLJP. Activated carbon derived from rice husk by NaOH activation and its application in supercapacitor. *Progress in Natural Science: Materials International.* 2014; 24(3): 191-8. doi: 10.1016/j.pnsc.2014.05.012.
- Al-Degs YS, El-Barghouthi MI, El-Sheikh AH, Walker GMJD. pigments, Effect of solution pH, ionic strength, and temperature on adsorption behavior of reactive dyes on activated carbon. 2008; 77(1): 16-23.
- Baccar R, Bouzid J, Feki M, Montiel AJJ. Preparation of activated carbon from Tunisian olive-waste cakes and its application for adsorption of heavy metal ions. *Journal of Hazardous Materials.* 2009; 162(2-3): 1522-9. doi: 10.1016/j.jhazmat.2008.06.041.
- Haile TM, Fuerhacker MJW. Simultaneous adsorption of heavy metals from roadway stormwater runoff using different filter media in column studies. *Water.* 2018; 10(9): 1160. doi: 10.3390/w10091160.

**Cite this article:** Al-Rub SSA, Alqahtani YS, Alqarni AO, Mahnashi MH, Alyami BA, Rezigue M. Removal and Reusability of Lead (II) from Aqueous Samples Using the Adsorption Method onto Commercial Activated Carbon: Kinetics and Thermodynamics Studies. *Indian J of Pharmaceutical Education and Research.* 2024;58(2):441-5.